

CHARACTERIZATION AND ELECTROCHEMISTRY OF LiFePO_4 SYNTHESIZED BY SONICATION- HYDROTHERMAL METHODS

Wagiyo Honggowiranto* and Evvy Kartini

Center for Science and Technology of Advanced Materials - BATAN
Kawasan PUSPIPTEK Serpong, Gd.71 Tangerang-Selatan, 15314

*E-mail: wagiyo@batan.go.id

Received: 28 September 2015

Revised: 23 November 2015

Accepted: 08 January 2016

ABSTRACT

CHARACTERIZATION AND ELECTROCHEMISTRY OF LiFePO_4 BY SONICATION-HYDROTHERMAL METHODS. Cathode materials of LiFePO_4 for rechargeable-lithium ion battery were synthesized by combination of sonication and hydrothermal method. The reaction has been carried out by mixing of $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$, H_3PO_4 , LiOH and ethylene glycol. The mixtures were sonicated by ultrasonic prior to a hydrothermal process. The crystal structure, microstructure and electrical properties of LiFePO_4 products were characterized by using X-ray diffraction (XRD), a Scanning Electron Microscope (SEM), and an Impedance Spectroscopy, respectively. The X-ray data showed that the crystal structure of LiFePO_4 belongs to the *P m n a* space group (olivine structure). The crystalline size of sample non-sonic, sonic and commercial LiFePO_4 were 730.2; 3068.0 and 639.4 Å, respectively. Performances of half cell batteries were measured by Impedance spectroscopy and by using Battery Analyzer BST-8. The EIS data from half cell batteries of non-sonic, sonic and commercial LiFePO_4 were 269.92; 149.85 and 106.2 Ω, respectively. Meanwhile, the specific capacities at 0.1C of non-sonic, sonic and commercial LiFePO_4 were 98.70; 120.17 and 125.23 mAh/g, respectively. As confirmed by SEM image, the particle distribution of sonic- LiFePO_4 were more homogenous, and had properties similar to the commercial ones. It is concluded that the sonication procedure carried out prior to hydrothermal has improved performance of the lithium ion battery.

Keywords: Lithium-ion Battery, LiFePO_4 cathoda, Sonication, Hydrothermal

ABSTRAK

KARAKTERISASI DAN ELEKTROKIMIA LiFePO_4 YANG DISINTESIS DENGAN METODE SONIKASI-HIDROTHERMAL. Telah dilakukan sintesis bahan katoda LiFePO_4 untuk baterai isi ulang ion-lithium dengan kombinasi sonikasi dan metode hidrotermal. Dengan mereaksikan campuran dari $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$, H_3PO_4 , LiOH dan etilena glikol. Campuran disonikasi dengan ultrasonik sebelum proses hidrotermal. Hasil sintesis dikarakterisasi masing-masing, struktur kristal dengan difraksi sinar-X (XRD), struktur mikro dengan *Scanning Electron Microscope (SEM)*, dan sifat listrik dengan Spektroskopi Impedansi (EIS). Dari data X-ray menunjukkan bahwa struktur kristal dari LiFePO_4 memiliki grup ruang *P m n a* (struktur olivin). Ukuran kristal dari sampel LiFePO_4 tidak-disonikasi, sonikasi dan komersial masing-masing sebesar 730,2; 3068 dan 639,4 Å. Unjuk kerja sel baterai impedan diukur dengan Spektroskopi Impedansi dan *charge/discharge* dengan *Battery Analyzer BST-8*. Dari data EIS diperoleh hasil impedansi baterai dari bahan LiFePO_4 tidak-disonikasi, sonikasi dan komersial masing-masing sebesar 269,92; 149,85 dan 106,2 Ω. Sedang hasil *charge/discharge* pada 0,1C diperoleh kapasitas-spesifik LiFePO_4 tidak-disonikasi, sonikasi dan komersial masing-masing sebesar 98,70; 120,17 dan 125,23 mAh/g. Hal ini juga ditunjukkan pada gambar *SEM* bahwa distribusi partikel LiFePO_4 hasil sonifikasi lebih homogen dan memiliki sifat yang mirip dengan komersial. Dengan demikian dapat disimpulkan bahwa sonifikasi sebelum hidrotermal telah meningkatkan kinerja baterai ion-lithium.

Kata kunci: Baterai ion-lithium, Katoda LiFePO_4 , Sonikasi, Hidrotermal

INTRODUCTION

Efficient low cost lithium ion battery methods are currently being developed for large scale manufacturing. Most of the research in lithium ion batteries are focusing on improvement of materials for cathodes and electrolytes for better performance and safety [1-3]. The different methods are researched to show the benefits of using lithium iron phosphate (LiFePO_4) as cathode material over other Li-ion based materials such as manganese or cobalt based lithium cathodes. Solid state reaction [4] co-precipitation [5], ball-milling and ball-milling microwave heating [6,7], doping and sol-gel [8] are various techniques being used to synthesize LiFePO_4 powders. However, some drawbacks, namely, poor electronic conductivity, low density, and low ionic diffusivity, which have limited its application [9]. The electronic conductivity [10] of LiFePO_4 is $\sim 10^{-9} \text{ S.cm}^{-1}$, it is much lower than that of LiCoO_2 ($\sim 10^{-3} \text{ S.cm}^{-1}$) and LiMn_2O_4 (2×10^{-5} - $5 \times 10^{-5} \text{ S.cm}^{-1}$) [11]. However, LiFePO_4 is a good Li ion battery cathode for its high theoretical capacity, cycle/thermal stability, and environmental benefits over other Li ion type batteries. The structure of LiFePO_4 is also shown to have an olivine structure providing a safer charging/discharging than other cathode materials. This material shows good theoretical capacity at 170mAh/g and a flat voltage of 3.4 V, but low conductivity is the major disadvantage of these types of cathodes [8,12].

Electronic conductivity of LiFePO_4 could be improved by carbon coating metal doping [13,14], and low ionic diffusivity may be improved through reduction of particle size. Previously, it was reported that particle sizes depend on the synthesis method and the media of preparation (pH, pressure, etc.) used [15]. One of the most relevant methods for reducing particle size was the hydrothermal method [16,17]. The hydrothermal method is also a simple method which involves low temperature reaction. The reaction temperature of hydrothermal synthesis of LiFePO_4 (LFP) was usually in exceed of 175°C to minimize iron disorder and to obtain material with correct lattice parameters and volume. Sonochemistry or sonication method is one of the earliest techniques used to prepare nanosized compounds. However, there were no studies that combine both the ultrasonic and hydrothermal methods on synthesizing LiFePO_4 . Therefore in the present work, the sonication method was performed prior to a hydrothermal process in order to obtain a more homogenous microstructure and better capacities. In order to confirm the crystal structure and microstructure the LiFePO_4 -sonic was characterized by X-ray diffraction and scanning electron microscope. Furthermore, performance of the battery was analyzed by impedance spectroscopy and battery analyzer. The results were compared with the commercial LiFePO_4 .

EXPERIMENTAL

Material Preparation

Cathode materials of LiFePO_4 were prepared via a sonication-hydrothermal process. The starting materials were $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$ (Sigma-Aldrich, 99.0%), H_3PO_4 (Aldrich, 85.0%), LiOH (Merck, 98.0%) and ethylene glycol (Merck, 99.5%), with mole ratio 3 : 1 : 1 : 1/3. First LiOH was dissolved in 60 mL of deionized water, H_3PO_4 , $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$. Ethylene glycol was added subsequently, with stirring to get suspension. In this study a sonication was applied for 30 minutes to homogenize the mixture prior to the hydrothermal process. After stirring and with/ without sonication, the mixed solution was transferred into a 90 mL home made teflon-lined stainless steel autoclave. It was sealed off tightly followed by heating in an electric muffle oven at temperatures of 180°C for 24 hours, then cooled down to room temperature. Details of the hydro thermal method has been described elsewhere [18,19]. The solid grey-green precipitates was filtered and washed several times with ethanol and distilled water and then dried at vacuum oven at 110°C for 10 hrs then heated at 600°C for 6 hrs.

Structural Characterization

For comparison, a commercial powder LiFePO_4 was used in the present work. The samples are then labelled as nonsonic- LiFePO_4 , sonic- LiFePO_4 and commercial- LiFePO_4 . The crystal structure of those LiFePO_4 were characterized by X-ray diffraction (XRD) using a PANalytical EMPYREAN Series-2, using $\text{Cu K}\alpha$, scan range from 10° to 80°. The morphology of the samples was observed by using Scanning Electron Microscopy (SEM, JSM-6510A).

Cathode Preparation

The cathode was prepared by mixing the active materials with artificial carbon and then grounding the mixture for 30 minutes. Polyvinylidene fluoride (PVDF) was dissolved in N-methyl-2-pyrrolidinone (NMP) solution using magnetic stirring and simultaneously heated at 80°C for 2 hours. The weight ratio of active materials with artificial carbon and PVDF was 85:10:5. The slurry was formed in the vacuum mixer for 1h, and the slurry was pasted onto an aluminum current collector using doctor blade. It was dried on oven vacuum at 110 °C for 10 hrs.

Cell Assembly and Electrochemical Testing

In the present work, three half-cell battery was prepared from LiFePO_4 nonsonication-hydrothermal/Li (nonsonic- LiFePO_4), sonication-hydrothermal/Li (sonic- LiFePO_4) and LiFePO_4 commercial/Li (commercial- LiFePO_4). All of half-cell battery were constructed inside

an argon filled glove box Vigor with the content of O_2 less than 1 ppm. The performance of battery was evaluated in CR2016 coin-type cells, using 20 mm diameter coin cells (CR2016) with Celgard 2500™ separator, Li (reference electrode) and electrolyte (1M LiPF_6 dissolved in ethylene carbonate (EC):dimethyl (DMC) 1:2 solution). The crimped coin cells were placed in a stainless steel cell (MTI Corporation) for electrochemical characterization. The impedance spectroscopy was done by LCR Hioki Tester. The charge–discharge experiment was conducted using a battery analyzer system (BTS-8, MTI, 5V/1mA) from 2.5 to 4.2V for several cycles at 0.1C.

RESULTS AND DISCUSSION

Materials Characterizations

The crystal structure of nonsonic, sonic and commercial- LiFePO_4 powders were analyzed by XRD to verify phase purity. The XRD results were illustrated in Figure 1(a), (b) and (c), respectively. In order to analyze the purity of the LiFePO_4 -sonic, the data was analyzed by using High Score Plus refinement application code. It was clear that the sonication process has increased the crystallinity of the LiFePO_4 , in comparison to the sample without sonication, with the average of crystallite size of 3068.0 Å. Meanwhile, non-sonic LiFePO_4 showed smaller crystallite sizes with the average of 730.2 Å, and higher background scattering.

Figure 1(b) and 1(c) showed the comparison of sonic- LiFePO_4 and commercial- LiFePO_4 . It is shown that sonic- LiFePO_4 has the identical XRD pattern with the commercial- LiFePO_4 . It can be seen here, that the

dominant diffraction peaks can be indexed as the orthorhombic LiFePO_4 phase with space group $Pnma$, according to the standard pattern of JCPDF 016-2282. It means that the synthesized LiFePO_4 via sonication-hydrothermal process was successfully formed and the phase was pure 100% LiFePO_4 . Similar result was observed for LiFePO_4 -commercial in Figure 1(c), with 100% pure LiFePO_4 . However, by close inspections, it is shown that there was a discrepancy between the sonic- LiFePO_4 and commercial- LiFePO_4 , such as the broadening of the crystalline Bragg peaks. The peaks belong to the sonic- LiFePO_4 are much sharper in comparison to the peaks of commercial- LiFePO_4 . As listed in Table 1, the crystallite sizes were 730.2 Å, 3068 Å and 639 Å for non-sonic, sonic and commercial- LiFePO_4 , respectively. The microstructures were observed by SEM shown in Figure 2(a), 2(b) and 2(c), for nonsonic, sonic and commercial- LiFePO_4 , respectively. Figure 2(a) showed that the particles of non sonic LiFePO_4 was agglomerated and not well distributed.

Similar result was observed for the microstructure of sonic and commercial- LiFePO_4 . For nonsonic LiFePO_4 the particle sizes were not well distributed. The morphologies are rather like hexahedral sheets, which resulted from the anisotropic surface energy of LiFePO_4 . On the microstructure of an LiFePO_4/C composite generated through sonication-hydrothermal showed a more uniform morphology compared with nonsonic- LiFePO_4 [20].

Electrochemical Characterizations

Before analyzing the battery performance, it was measured by impedance spectroscopy. The EIS results

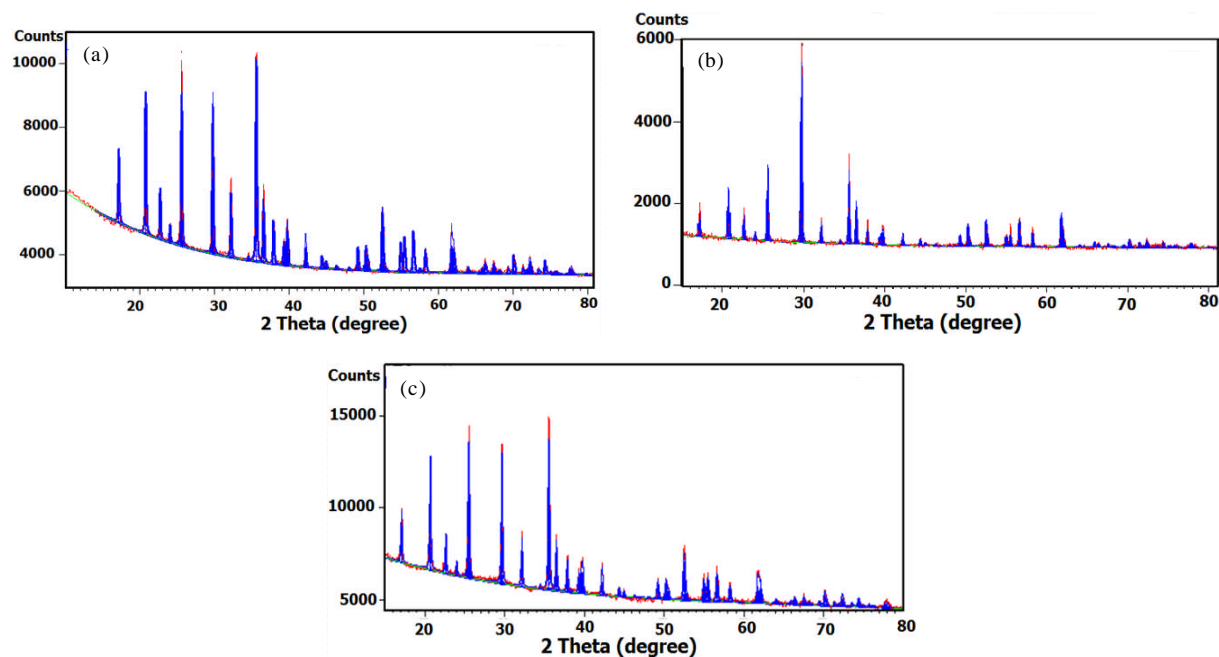


Figure 1. (a). The XRD patterns of (a). nonsonic- LiFePO_4 (b). sonic- LiFePO_4 and (c). commercial- LiFePO_4 .

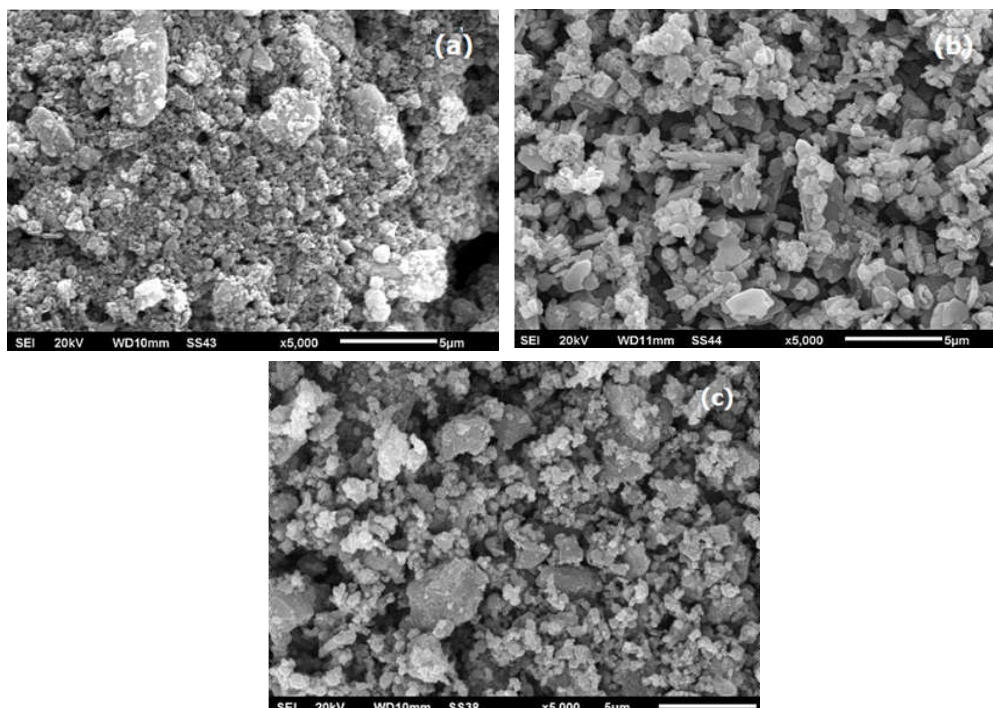


Figure 2. The SEM image of (a). nonsonic-LiFePO₄, (b). sonic-LiFePO₄ and (c). commercial-LiFePO₄

Table 1. Crystal structure analysis of nonsonic, sonic and commercial-LiFePO₄

	Nonsonic- hydrothermal	Sonic-hydrothermal	Powder Commercial
Formula /Unit Crystal	Li ₄ Fe ₄ O ₁₆	Li ₄ Fe ₄ O ₁₆	Li ₄ Fe ₄ O ₁₆
Formula mass (g/mol)	631.0376	631.0376	631.0376
Calculate Density (g/cm ³)	3.5892	3.6011	3.6072
Weight Fraction (%)	100	100	100
Space group (No.)	P n m a (62)	P n m a (62)	P n m a (62)
Lattice Parameters :			
a (Å)	10.3295(4)	10.3390(4)	10.3169 (4)
b (Å)	6.0056 (2)	6.0032 (2)	6.0018 (2)
c (Å)	4.7010(2)	4.6921 (2)	4.6908 (2)
FWHM (2Th=35.57°)	0.1665	0.1063	0.1763
alpha (o)	90	90	90
beta (o)	90	90	90
gamma (o)	90	90	90
Preferred Orientation	1.020686		
Parameters and Direction			
[0 0 1]	0.743721		
[0 1 0]	0.984201		
[0 1 0]			
Crystallite Size (Å)	730.2	3068.0	639.4
% Strain	0.000	0.028	0.008
Formula /Unit Crystal	Li ₄ Fe ₄ O ₁₆	Li ₄ Fe ₄ O ₁₆	Li ₄ Fe ₄ O ₁₆
Formula mass (g/mol)	631.0376	631.0376	631.0376
Calculate Density (g/cm ³)	3.5892	3.6011	3.6072
Weight Fraction (%)	100	100	100
Space group (No.)	P n m a (62)	P n m a (62)	P n m a (62)
Lattice Parameters :			
a (Å)	10.3295(4)	10.3390(4)	10.3169 (4)
b (Å)	6.0056 (2)	6.0032 (2)	6.0018 (2)
c (Å)	4.7010(2)	4.6921 (2)	4.6908 (2)

of non-sonic, sonic and commercial- LiFePO₄ are shown in Figure 3. The intercept on X-axis in the high frequency region indicates an internal resistance of the cell, and the diameter of the semicircle represents the effect caused by charge transfer and electrochemical double layer. The straight line at a 45° angle after the semicircle represents the resistance in the bulk electrode [21]. From the data

shown in Figure 3, it is shown that the impedance of commercial-LiFePO₄ was lower than both sonic and nonsonic LiFePO₄. However, by close inspection it becomes clear that there was slightly different of resistant between the sonic and commercial-LiFePO₄, namely 149.85 Ω and 106.2 Ω, respectively, mean while the non-sonic LiFePO₄ was about 269.92 Ω. It means that the

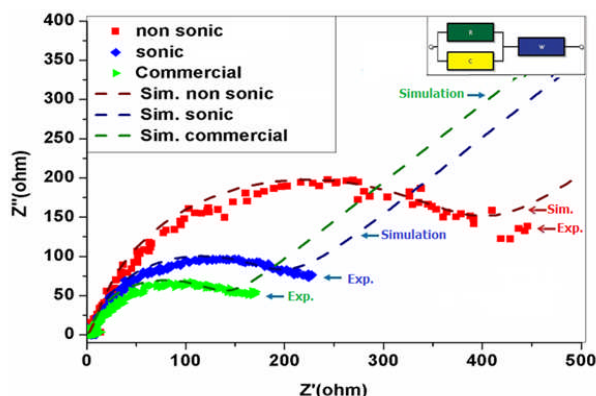


Figure 3. Impedance plots of half cells of non-sonic, sonic and commercial- $\text{LiFePO}_4/\text{Li}$

sonic- LiFePO_4 has better electronic conductivity compared to the nonsonic ones (Table 2) [22].

Table 2. Resistance and specific capacities of nonsonic, sonic and commercial.

Battery lithium ion	R (Ω)	W ($\Omega \cdot \text{s}^{-2}$)	Specific Capacity (mAh/g)
nonsonic- $\text{LiFePO}_4/\text{Li}$	269.92	1728.2	98.70
sonic- $\text{LiFePO}_4/\text{Li}$	149.85	1128.3	120.17
commercial- $\text{LiFePO}_4/\text{Li}$	106.2	939.61	125.23

The effects of carbonaceous materials on the physical and electrochemical performance of LiFePO_4 are reviewed by Kang Fei-Yu et al [23]. The introduction of an in-situ grown carbon coating would be beneficial to limiting the LiFePO_4 growth and increasing the electric conductivity. The structure and precursors of the in-situ grown carbons have a great influence in the rate performance of the hybrids, which can be related to an improved electron and ion transfer rate. In this case, the addition of ethylene glycol as a carbon source would affect the ionic conductivity and ion transport. Though, the crystal growth could not be limited, due to the sonication prior to hydrothermal process. Furthermore, performance of half-cells of nonsonic, sonic and commercial LiFePO_4 with the counter electrode lithium metal, Li, were analyzed by using battery analyser. Fig.4(a), 4(b) and 4(c) showed charge discharges of nonsonic- $\text{LiFePO}_4/\text{Li}$, sonic- $\text{LiFePO}_4/\text{Li}$ and commercial - $\text{LiFePO}_4/\text{Li}$, respectively. The characteristic showed a flat discharge plateau at around 3.2 V, which represents a LiFePO_4 working voltage. The charge discharge processes were done for 10 cycles at 0.1 C.

The specific capacity of lithium ion battery made from nonsonic and sonic- LiFePO_4 were 98.7 and 120.17 mAh/g, respectively, meanwhile from commercial LiFePO_4 was 125.23 mAh/g, at 0.1C. It is concluded that the sonication prior to hydrothermal has improved performance of the lithium ion battery or similar performance as the commercial ones.

In order to achieve an excellent electrochemical performance of LiFePO_4 , it is necessary to take advantage

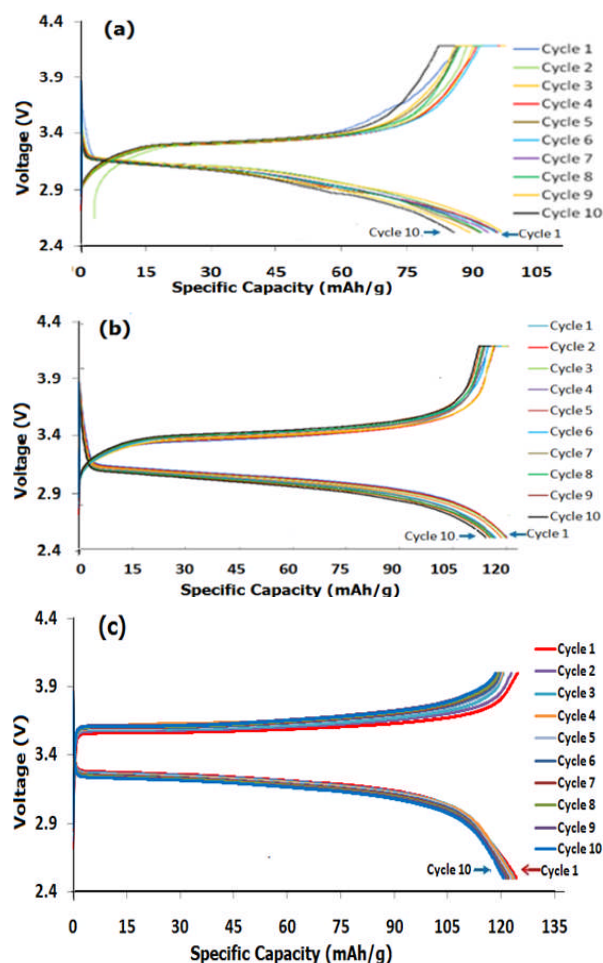


Figure 4. (a). Specific capacity of (a). nonsonic- $\text{LiFePO}_4/\text{Li}$, (b). sonic- $\text{LiFePO}_4/\text{Li}$ and (c). commercial- $\text{LiFePO}_4/\text{Li}$.

of and to combine these approaches to optimize electron and ion transfer rates. Also, it is most important to minimize the carbon content in LiFePO_4 carbon hybrids to increase volumetric energy density. The primary particle size that determines electrochemical performance, including cycling, rate capability, and low-temperature performance, could be successfully controlled via this method.

The cyclic performances after 10th cycles for nonsonic, sonic and commercial- $\text{LiFePO}_4/\text{Li}$ were shown in Fig. 5 to observe its capacity retentions. The nonsonic- $\text{LiFePO}_4/\text{Li}$ showed the first discharge at 98.70 mAh/g then decreased to 81.16 mAh/g after 10th cycles or decreased about 17.7%. The sonic- $\text{LiFePO}_4/\text{Li}$ showed the first discharge at 120.17 mAh/g then decreased to 114.26 mAh/g after 10th cycles or decreased about 4.90%. For the commercial $\text{LiFePO}_4/\text{Li}$, the first discharge at 125.23 mAh/g and decreased to 120.64 mAh/g for the 10th cycles which was about 3.70%. The capacity retentions of the sonic- LiFePO_4 is rather similar to the commercial ones. It is shown that the sonication prior to hydrothermal process improved performance of the lithium ion batteries.

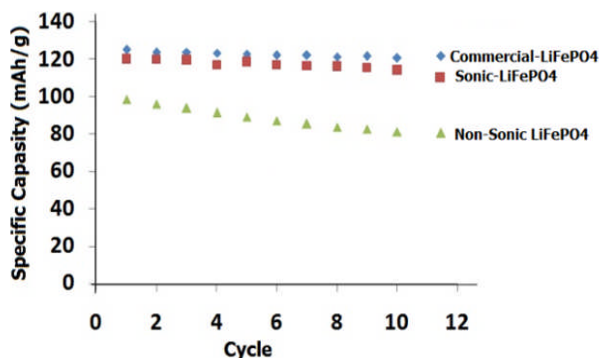


Figure 5. Cycling performance of nonsonic, sonic and commercial-LiFePO₄/Li.

CONCLUSION

LiFePO₄ as cathode material for Li-ion battery was successfully synthesized by sonication-hydrothermal method. The addition of ethylene glycol during sonication had increased the electronic conductivity since it became a source of carbon. The charge-discharge results show that both sonic and commercial-LiFePO₄ showed good performance of the lithium ion battery, but the specific capacity was slightly higher for commercial LiFePO₄. In this case, the highest specific capacity obtained for sample prepared by sonication-hydrothermal was 120.70 mAh/g, while from commercial was 125.23 mAh/g at 0.1C. It was assumed that the crystallite sizes as the results of the hydrothermal process had affected performance of the electrical conductivity and also the battery. The sonication prior to hydrothermal has also proved the growth of the LiFePO₄ crystal more homogenous due to smaller particles of the raw material mixtures. It is concluded that the sonication prior to hydrothermal has improved performance of the lithium ion battery.

For further study, it is important to understand the temperature effect of sonication-hydrothermal methods for the nucleation rate of the LiFePO₄ crystal. The primary particle size that determines electrochemical performance, including, rate capability, and low temperature performance, could be successfully controlled via this method. Hence, this would be the most promising method for commercial production of LiFePO₄/C directed to hybrid electrical vehicles and pure electrical vehicle market.

ACKNOWLEDGEMENTS

This work was partially supported from the Ministry Research Technology and Higher Education (KEMENRISTEKDIKTI) and the Advanced Materials Division, Science and Technology for Advanced Materials, National Nuclear Energy Agency (PSTBM-BATAN), Indonesia, through the Insentif SINAS 2015 and a DIPA 2015.

REFERENCES

- [1]. N. I. P. Ayu, E. Kartini, L. D. Prayogi, *et.al.* "Crystal structure analysis of Li₃PO₄ powder prepared by wet chemical reaction and solid-state reaction by using X-ray diffraction (XRD), *submitted/under review.*
- [2]. B. Priyono, A. Z. Syahrial, E. Kartini, *et.al.* "Synthesis Of Lithium Titanate (Li₄Ti₅O₁₂) Through Hydrothermal Process By Using Lithium Hydroxide (LiOH) And Titanium Dioxide (TiO₂) Xerogel." *Int. J. Technol.*, vol. 4, pp. 555-564, 2015.
- [3]. E. Kartini, M. Nakamura, M. Arai, *et.al.* "Structure and dynamics of solid electrolyte (LiI)_{0.3}(LiPO₃)_{0.7}." *Solid State Ionics*, vol. 262, pp. 833-836, 2014.
- [4]. J. Li, S.-H. Yao, H.-M. Zhou, and W.-J. Geng. "Preparation of LiMn_{0.4}Fe_{0.6}PO₄/C Composite by A New Route Combining Solid-state Reaction with Hydrothermal Synthesis." *J. Inorg. Mater.*, vol. 29, no. 4, pp. 443-448, 2014.
- [5]. M. S. Song, Y. M. Kang, J. H. Kim, *et.al.* "Simple and fast synthesis of LiFePO₄-C composite for lithium rechargeable batteries by ball-milling and microwave heating," *J. Power Sources*, vol. 166, pp. 260-265, 2007.
- [6]. C. Sato, E. Hoshi, K. Uematsu, *et.al.* "Hydrothermal Reaction by Microwave Heating for Synthesis of LiFePO₄ as Cathode Material," *Trans. Mater. Res. Soc. Japan*, vol. 35, no. 2, pp. 397-400, 2010.
- [7]. Y. Hu, J. Yao, Z. Zhao, *et.al.* "ZnO-doped LiFePO₄ cathode material for lithium-ion battery fabricated by hydrothermal method," *Mater. Chem. Phys.*, vol. 141, no. 2-3, pp. 835-841, 2013.
- [8]. Z. Yang and S. Wang. "High Cycling Performance Cathode Material/ : Interconnected LiFePO₄ / Carbon Nanoparticles Fabricated by Sol-Gel Method." *J. Nanomater.*, vol. 2014, pp. 1-7, 2014.
- [9]. Y. Lou, J. Zhang, L. Zhu, and L. Lei. "An Alternative Synthesis Route of LiFePO₄-Carbon Composites for Li-Ion Cathodes." *J. Nanomaterials*, vol. 2013, pp 1-6, 2013.
- [10]. B. Jin, G. E. Sun, H. Gu, and Q. Jiang. "Processing Research Synthesis and electrochemical properties of LiFePO₄/MWCNT nanocomposites for rechargeable lithium-ion batteries." *Processing*, vol. 11, no. 5, 2010.
- [11]. H. Xu, J. Sun, and L. Gao. "Hydrothermal synthesis of LiMnO₂ microcubes for lithium ion battery application." *Ionics (Kiel)*, vol. 19, pp. 63-69, 2013.
- [12]. E. Kartini, M. F. Collins, F. Mezei, and E. C. Svensson, "Neutron scattering studies of glassy and liquid ZnCl₂," *Phys. B Condens. Matter*, vol. 241-243, pp. 909-911, 1997.
- [13]. J. Wang and X. Sun. "Understanding and recent development of carbon coating on LiFePO₄ cathode materials for lithium-ion batteries." *Energy Environ. Sci.*, vol. 5, pp. 5163-5185, 2012.

- [14]. C. Ajpi, G. Diaz, H. Visbal, and K. Hirao. "Synthesis and characterization of Cu-doped LiFePO₄ with/without carbon coating for cathode of lithium-ion batteries." *J. Ceramic Society Japan*, pp. 441-443, 2013.
- [15]. Q. Song, X. Ou, L. Wang, G. Liang, and Z. Wang. "Effect of pH value on particle morphology and electrochemical properties of LiFePO₄ by hydrothermal method." *Mater. Res. Bull.*, vol. 46, no. 9, pp. 1398-1402, 2011.
- [16]. F. Lu, Y. Zhou, J. Liu, and Y. Pan. "Enhancement of F-doping on the electrochemical behavior of carbon-coated LiFePO₄ nanoparticles prepared by hydrothermal route." *Electrochim. Acta*, vol. 56, pp. 8833-8838, 2011.
- [17]. H. Xu, B. W. Zeiger, and K. S. Suslick, "Sonochemical synthesis of nanomaterials.," *Chem. Soc. Rev.*, vol. 42, pp. 2555-67, 2013.
- [18]. W. Honggowiranto, E. Kartini. "Sonication-Hydrothermal Synthesis of LiFePO₄ For Lithium-Ion Battery." presented at the 20th International Seminar on Solid State Ionics, Keystone, Colorado, USA, 2015.
- [19]. X. Qin, J. Wang, J. Xie, F. Li, L. Wen, and X. Wang. "Hydrothermally synthesized LiFePO₄ crystals with enhanced electrochemical properties: simultaneous suppression of crystal growth along [010] and antisite defect formation." *Phys. Chem. Chem. Phys.*, vol. 14, p. 2669, 2012.
- [20]. J. Liu, Z. Wang, G. Zhang, Y. Liu, and A. Yu. "Size-Controlled Synthesis of LiFePO₄/C Composites as Cathode Materials for Lithium Ion Batteries." *Int. J. Electrochem. Sci.*, vol. 8, pp. 2378-2387, 2013.
- [21]. G. Talla, R. K. Guduru, B. Q. Li, and P. S. Mohanty, "Doped-Si-Ag composite electrodes for Li-ion batteries," *Solid State Ionics*, vol. 269, pp. 8-13, 2015.
- [22]. C. Sun, S. Rajasekhara, Y. Dong, *et.al.* "Hydrothermal Synthesis and Electrochemical Properties of Li₃V₂(PO₄)₃/C-Based Composites for Lithium-Ion Batteries." *ACS Appl. Mater. Interfaces*, vol. 2, pp. 3772-3776, 2011.
- [23]. K. Fei-yu, M. a Jun, and L. I. Bao-hua. "Effects of carbonaceous materials on the physical and electrochemical performance of a LiFePO₄ cathode for lithium-ion batteries." *New Carbon Mater.*, vol. 26, no. 11, pp. 161-170, 2011.