

FORMATION OF SPINEL STRUCTURE IN SYNTHESIS PROCESS OF $\text{Li}_{1.37}\text{Mn}_2\text{O}_4$ USING HYDROTHERMAL METHOD

Ibrahim Purawiardi and Ety Marti Wigayati

Research Center for Physics - LIPI

Kawasan Puspiptek, Serpong 15314, Tangerang Selatan

email: ettymw@yahoo.com

Received: 2 August 2018

Revised: 31 August 2018

Accepted: 14 September 2018

ABSTRACT

FORMATION OF SPINEL STRUCTURE IN SYNTHESIS PROCESS OF $\text{Li}_{1.37}\text{Mn}_2\text{O}_4$ USING HYDROTHERMAL METHOD $\text{Li}_{1.37}\text{Mn}_2\text{O}_4$ is one form of $\text{Li}_{1+x}\text{Mn}_2\text{O}_4$ which is engineered from LiMn_2O_4 phase which is commonly used as a lithium cathode active ingredient. The crucial thing from $\text{Li}_{1.37}\text{Mn}_2\text{O}_4$ synthesis is the spinel structure that is formed. This study aims to observe when the spinel structure of $\text{Li}_{1.37}\text{Mn}_2\text{O}_4$ starts and when the transformation from a tetragonal structure into spinel occurs. The raw materials used are tetragonal LiOH and tetragonal MnO_2 . The synthesis was carried out using a hydrothermal method with a temperature of $200\text{ }^\circ\text{C}$ with a variation of holding times of 50, 70, 90 and 110 hours. Observation of spinel structure was carried out using XRD and TEM. The results obtained were at the holding times of 50 and 70 hours, the spinel structure had not been formed. The spinel structure begins to form at 90 hours holding time which also indicates that the transformation from the tetragonal structure to spinel occurs at such holding time. The result of a 90-hour holding time is a regular spinel structure but there are still many Mn and Mn-O based impurities. While the results of the 110-hour holding time produce a perfect yet irregular transformation of the spinel structure.

Keywords: $\text{Li}_{1.37}\text{Mn}_2\text{O}_4$, Spinel, Crystal structure, Hydrothermal

ABSTRAK

PEMBENTUKAN STRUKTUR SPINEL PADA PROSES SINTESIS $\text{Li}_{1.37}\text{Mn}_2\text{O}_4$ MENGGUNAKAN METODE HIDROTHERMAL. $\text{Li}_{1.37}\text{Mn}_2\text{O}_4$ merupakan salah satu bentuk dari $\text{Li}_{1+x}\text{Mn}_2\text{O}_4$ yang merupakan rekayasa dari fasa LiMn_2O_4 yang biasa digunakan sebagai bahan aktif katoda baterai lithium. Hal krusial dari sintesis $\text{Li}_{1.37}\text{Mn}_2\text{O}_4$ adalah struktur spinel yang terbentuk. Studi ini bertujuan untuk mengamati kapan mulai terbentuknya struktur spinel $\text{Li}_{1.37}\text{Mn}_2\text{O}_4$ dan kapan transformasi dari struktur tetragonal menjadi spinel terjadi. Bahan baku yang digunakan adalah LiOH tetragonal dan MnO_2 tetragonal. Sintesis dilakukan menggunakan metode hidrotermal dengan temperatur $200\text{ }^\circ\text{C}$ dengan variasi waktu penahanan 50, 70, 90 dan 110 jam. Pengamatan struktur spinel dilakukan menggunakan XRD dan TEM. Hasil yang diperoleh adalah pada waktu penahanan 50 dan 70 jam struktur spinel belum terbentuk. Struktur spinel mulai terbentuk pada waktu penahanan 90 jam yang menandakan juga bahwa transformasi dari struktur tetragonal menjadi spinel terjadi pada waktu penahanan tersebut. Hasil dari waktu penahanan 90 jam adalah struktur spinel yang teratur namun masih ditemukan banyak impuritas berbasis Mn dan Mn-O. Sementara hasil dari waktu penahanan 110 jam menghasilkan transformasi sempurna struktur spinel namun tidak teratur.

Kata kunci: $\text{Li}_{1.37}\text{Mn}_2\text{O}_4$, Spinel, Struktur kristal, Hidrotermal

INTRODUCTION

LiMn_2O_4 is one of the materials used as cathode lithium active material. LiMn_2O_4 has a relatively inexpensive price and good thermal stability, but has a weakness on low specific capacities [1,2]. For this reason,

various efforts have been made by scientists to increase their specific capacity, one of which is to convert it to $\text{Li}_{1+x}\text{Mn}_2\text{O}_4$. The $\text{Li}_{1+x}\text{Mn}_2\text{O}_4$ cathode is engineered from LiMn_2O_4 which has more lithium content. This cathode

type is included in the category of lithium-rich cathode oxides. Lithium-rich cathode oxides are candidates for new generation of cathode lithium batteries with the superiority of oxidation-reduction reactions of transition metals (cations) and multivalent anions so that theoretically it potentially produces a higher specific capacity compared to the usual lithium oxide cathode [3]. However, the weakness of this material is a less stable cyclic behavior. Therefore efforts to improve the current cycle behavior are mostly done by increasing the composition of the spinel structure and modifying its particle surface [4], where these two crucial things depend heavily on the synthesis method used.

Basically, the synthesis method of $\text{Li}_{1+x}\text{Mn}_2\text{O}_4$ is the same as that of LiMn_2O_4 . Such synthesis method includes solid reaction with raw materials of Li_2CO_3 and MnO_2 calcined in two stages 500 °C and 780 °C [5], solid reactions with raw materials of $\alpha\text{-MnO}_2$ nanotubes and Li_2CO_3 calcined at 900 °C [6], sol-gel with calcination temperature of 650 °C [7], dynamic process [8], combustion method with a temperature of 800 °C [9], synthesis method with precursor polyvinylpyrrolidone or poly (vinyl alcohol) [10], a combination of mechanical alloying and rotating heating methods [11], etc.

The composition of the spinel structure on LiMn_2O_4 cathode will affect the performance of lithium batteries. The greater the spinel composition, the specific capacity will increase due to a decrease in irreversible capacity loss [12]. Irreversible capacity loss is a phenomenon where some lithium ions do not return to the spinel structure during the discharging process before being extracted during the charging process.

This study attempts to synthesize $\text{Li}_{1+x}\text{Mn}_2\text{O}_4$ with a spinel structure in the form of $\text{Li}_{1.37}\text{Mn}_2\text{O}_4$ from the raw material of tetragonal LiOH and tetragonal MnO_2 using the hydrothermal method. A crucial problem in this synthesis is when the spinel structure begins to form and when the transformation of the tetragonal structure into spinel begins to occur. The spinel structure has an indication of having a Fd-3m space group [13]. Therefore, controlling the formation of Fd-3m space group is the main objective of this synthesis.

EXPERIMENT METHOD

Materials and Equipment

The raw materials used are tetragonal LiOH (Merck, purity > 99%) and tetragonal MnO_2 (Merck, purity > 99%).

Synthesis equipment used is magnetic stirrer and Morey type autoclave. While the characterization equipment used is the Rigaku Smart Lab XRD 3 kW in continuous scan mode with an angle range of 2θ from 10° to 90° and step width of 0.02°. The TEM used is Tecnai G2-STWIN FEI with an acceleration voltage of 200 kV and uses bright plane mode.

Procedure

$\text{Li}_{1.37}\text{Mn}_2\text{O}_4$ synthesis in this study follows the ideal reaction equation as follows:

LiOH and MnO_2 are mixed and dissolved using distilled water and added carbon black (purity > 99%) then stirred with a magnetic stirrer for one hour to produce slurry solution. The slurry solution was then put into an autoclave with a volume of 50 cc and heated with a temperature of 200 °C with a variation of holding time of 50 hours, 70 hours, 90 hours and 110 hours. After heating, the samples are removed from the autoclave to be dried in an oven at a temperature of 100 °C.

The samples are then characterized using X-ray diffractometer (XRD) and transmission electron microscope (TEM).

RESULTS AND DISCUSSION

Spinel structure is one variant of the cubic structure with certain crystal planes such as (111), (220), (311), (400), (331), (422), (511), (333), (440), (531) and (620) [14]. The spinel structure in this system has Fd-3m space group [13]. The X-ray diffraction pattern in Figure 1 shows that the spinel structure has not been formed at 50 and 70 hours of holding time. However, the spinel structure has been detected at 90 and 110 hours of holding time (see Figure 1). Spinel crystal planes detected at 90 hours of holding time are (111), (220), (311) and (440) while at 110 hours of holding time are (111), (311), (400) and (440) (as seen in Figure 1, Tables 1 and 2). Both the 90-hour and 110-hour holding times found three similarities in the crystalline plane formed, namely (111), (311) and (440). The difference between the two is that at the holding time of 90 hours, a plane (220) is found, while at the holding time of 110 hours, the plane (220) does not appear and a new plane (400) is found.

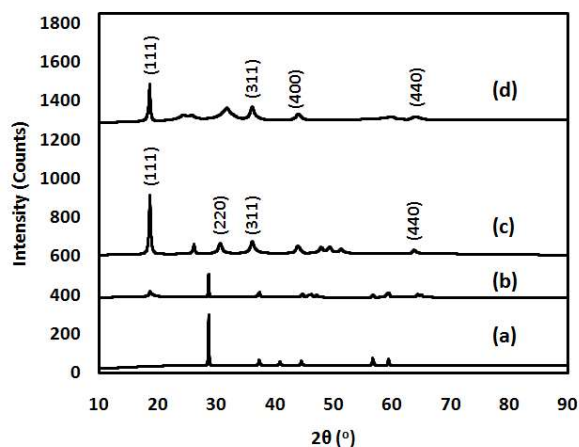


Figure 1. X-ray diffraction pattern in hydrothermal synthesis samples with a temperature of 200 °C along with Miller index in the emerging spinel structure planes (a). 50-hour holding time (b). 70-hour holding time (c). 90-hour holding time (d). 110-hour holding time.

Table 1. Identification of spinel structure on the samples with a 90-hour holding time.

2θ (°)	$\text{Sin}^2\theta$	$(\text{Sin}^2\theta)/3$	$(\text{Sin}^2\theta)/8$	$(\text{Sin}^2\theta)/11$	$(\text{Sin}^2\theta)/32$	hkl	a (Å)
18.620000	0.026171	0.008724	0.003271	0.002379	0.000818	111	8.253951
30.610571	0.069676	0.023225	0.008709	0.006334	0.002177	220	8.260742
36.070000	0.095851	0.031950	0.011981	0.008714	0.002995	311	8.258741
63.700000	0.278464	0.092821	0.034808	0.025315	0.008702	440	8.264292

Table 2. Identification of spinel structure on the samples with a 110-hour holding time.

2θ (°)	$\text{Sin}^2\theta$	$(\text{Sin}^2\theta)/3$	$(\text{Sin}^2\theta)/11$	$(\text{Sin}^2\theta)/16$	$(\text{Sin}^2\theta)/32$	hkl	a (Å)
18.61	0.026144	0.008715	0.002377	0.001634	0.000817	111	8.258347
36.06	0.095799	0.031933	0.008709	0.005987	0.002994	311	8.260955
43.93	0.139906	0.046635	0.012719	0.008744	0.004372	400	8.244367
63.81	0.279325	0.093108	0.025393	0.017458	0.008729	440	8.251546

When a lattice parameter values are plotted of all spinel planes detected in Table 1 against the Nelson-Riley function [15], a linear regression line will be obtained with a gradient of -0.001053 and interception of 8.266664 (Figure 2(a)). The linear regression line has an R2 value of 0.899057. That line can still be fixed so that it has a R2 value above 0.9 by dividing the two combinations of spinel constituent planes into groups (440), (311) and (111) (Figure 2(b)) and (440), (220) and (111) (Figure 2(c)) so that we can obtain two different cut off points, i.e. 8.266219 (Figure 2(b)) and 8.267704 (see Figure 2(c)). The cut off point in the linear regression line shows the precision lattice parameter value a_0 [14]. Thus, it can be assumed that there are two order-cell

spinel structures that are ordered in the sample resulted from 90 hours of holding time, each of which has a grid parameter of 8.266219 Å and 8.267704 Å.

Although the spinel structure is formed at 90-hour holding time, Mn-O and Mn-based impurities are still found. The first impurity phase was an orthorhombic-structured non-hausmanite Mn_3O_4 characterized by identification of d values of 3.41 Å, 1.84 Å and 1.78 Å (PDF # 75-0765). The second impurity phase is a primitive-cubic-structured Mn with detected d value of 1.90 Å (PDF # 33-0887). This shows that the function of carbon black as a reaction catalyst to prevent the formation of the Mn-O-based impurity phase has not functioned optimally at this 90-hour holding time.

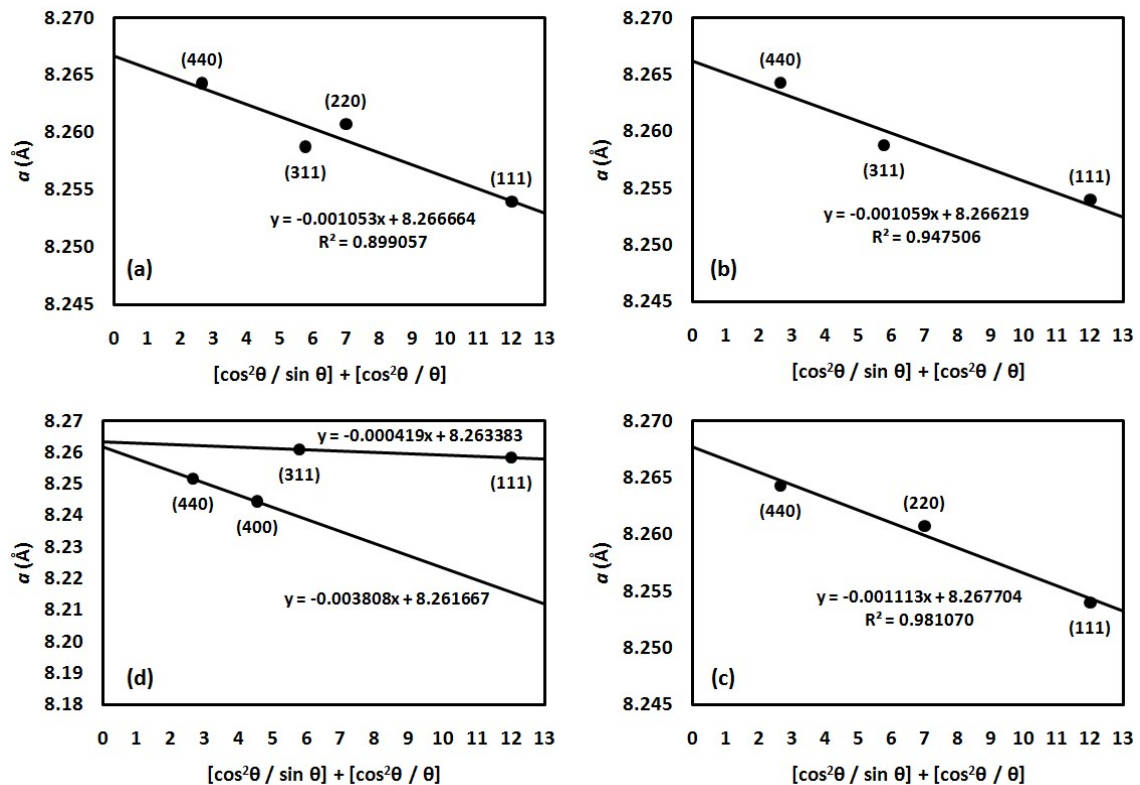


Figure 2. The plot of the lattice parameter a spinel structure as a function of $(\cos^2\theta/\sin\theta) + (\cos^2\theta/\theta)$ (a). 90-hour holding time with spinel planes (440), (311), (220), and (111) (b). 90-hour holding time with spinel planes (440), (311) and (111) (c). 90-hour holding time with spinel planes (440), (220), and (111) (d). 110-hour holding time.

With the discovery of the impurity phases of Mn_3O_4 and Mn, it can be as-certained even though the spinel structure is formed under ordered conditions, the results obtained were not $Li_{1.37}Mn_2O_4$ but experienced a deficiency of Mn to be $Li_{1.37}Mn_2O_4$.

Thus, it is very likely that the loss of some Mn occupancy in the spinel structure will be filled by Li atoms which are indeed made more in composition so that the spinel structure resembles the form of $LiMn_2O_4$ spinel. However, as some of Li functions change to fill Mn occupancy, it is feared that it will reduce the effectiveness of Li intercalation-deintercalation so that the initial function of adding Li from $LiMn_2O_4$ to $Li_{1.37}Mn_2O_4$ in order to increase the specific capacity of lithium batteries will not be achieved.

Meanwhile, when a lattice parameter values are plotted in Table 2 against Nelson-Riley function [16], a linear regression line formed by a minimum of three spinel constituent planes will not be obtained. However, if we extrapolate the linear regression line by grouping each of the two constituent planes, namely group (111) with (311) and group (400) with (440), an interception point will be found between the two linear regression lines at almost the same range, i.e. 8.26 (see Figure 2(d)). This shows that indeed there is actually a spinel structure with a precision lattice parameter of about 8.26 Å in the

synthesis result with 110-hour holding time, but the condition is a disorder. This disorder condition shows that even though the spinel structure is formed, the occupancy arrangement of Li, Mn and O atoms is messy and there is a possibility of exchanging positions with each other [14]. However, even though the spinel structure formed is in a disorder condition, the impurity based on Mn-O and Mn is no longer found. It shows the function of the carbon black as a reaction catalyst to prevent the emergence of Mn-O based phase to work well at this 110-hour holding time. The first impurity that appears in the synthesis results at a 110-hour holding time is C60 carbon with an indication of d values of 2.81 Å and 1.53 Å (PDF # 79-1715). While the second impurity is d at 3.44 Å which is assumed to be a transition phase between C60 with a cubic structure (d = 3.40 Å, PDF # 79-1715) and C70 with a hexagonal structure (d = 3.46 Å, PDF # 48-1206). The presence of carbon-based impurity shows that at 110-hour holding time, the amorphous carbon black structure undergoes a recrystallization process towards the crystalline form.

Thus, it is difficult to determine the best holding time parameters for the formation of $Li_{1.37}Mn_2O_4$ spinel structures by hydrothermal synthesis method at a temperature of 200 °C. From the point of view of the spinel crystal structure formed, a 90-hour holding time

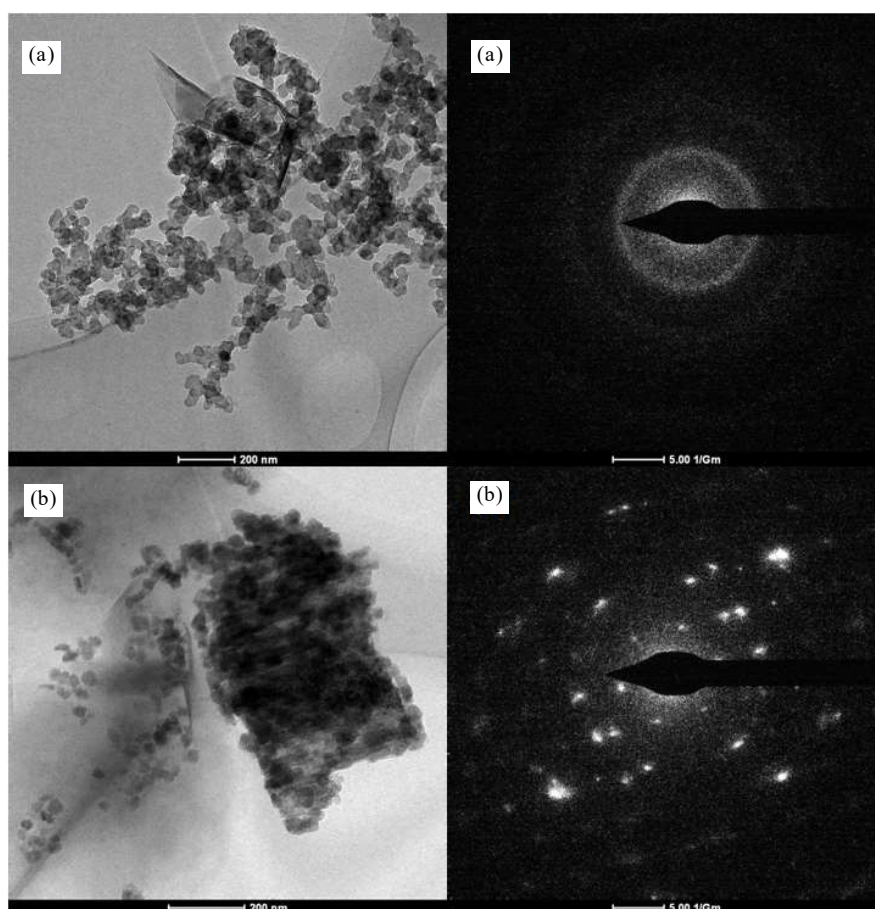


Figure 3. Images of TEM and SAED on hydrothermal synthesis particles with a temperature of 200 °C and a holding time of 90 hours.

is more recommended. This reasoning is strengthened from the results of TEM testing, where apart from obtaining nanoscale spinel crystallites (see Figure 3), the SAED diffraction pattern is clearly obtained in polycrystalline form (see Figure 3(a) on the right) and in the form of single crystalline (see Figure 3(b) on the right). The SAED single crystalline pattern of spinel structures cannot be found in synthesized spinel disorder structures with a holding time of 110 hours and only found in synthesis results with a 90-hour holding time. This pattern (see Figure 3(b) on the right) is identical to the arrangement of atoms forming the LiMn_2O_4 spinel structure, especially in the first ring which is identical to the arrangement of Mn and O at the viewpoint of $\{001\} \langle 100 \rangle$ and $\{010\} \langle 001 \rangle$ (see the simulation in Figure 4 then compare with Figure 3.b on the right).

Meanwhile, at holding times of 50 and 70 hours, the phase formed is a MnO_2 tetragonal which is indicated by the detected d values (PDF # 81-2261). At the 50-hour holding time, d values are detected namely 3.11 Å, 2.41 Å, 2.21 Å, 1.62 Å and 1.55 Å. While at 70-hour holding time, detected d values include 3.11 Å, 2.40 Å, 1.96 Å, 1.62 Å, 1.55 Å and 1.44 Å. Thus, at the 90-hour holding time there is a transformation of the crystal structure from tetragonal to cubic spinel.

CONCLUSION

The transformation of tetragonal structure into $\text{Li}_{1.37}\text{Mn}_2\text{O}_4$ spinel has been successfully synthesized

using a hydrothermal process at 200 °C with a holding time of 90 hours. At 90-hour holding time, the spinel structure is formed under order conditions, but there are still Mn and Mn-O-based impurities. At 110-hour holding time, Mn and Mn-O-based impurities are no longer found so that the synthesis takes place completely and produces $\text{Li}_{1.37}\text{Mn}_2\text{O}_4$ spinel structure, but the spinel structure that is formed has a disorder condition.

ACKNOWLEDGEMENT

The author would like to thank the 2018 Sinas Funding Research Incentive Program, upon the conduct of this research which is part of the research on “Lithium Extraction from Indonesian natural materials as raw material for Lithium batteries”, and Research Center for Physics - LIPI for XRD and TEM test equipment facilities.

REFERENCES

- [1] R. A. Rodriguez, E. L. Perez-Cappe, Y. M. Laffita, A. C. Ardanza, J. S. Salazar, M. A. Santos, M. A. A. Frutis, N. D. S. Mohalem, O. L. Alves. “Structural Defects in LiMn_2O_4 Induced by Gamma Radiation and its Influence on the Jahn-Teller Effect”, *Solid State Ionics*, Vol. 324, pp. 77-86, Jun. 2018.
- [2] H. Ren, Y. Q. Guo, Z. L. Chen, X. H. Zhang, Z. F. Zhang, Y. T. Li, Q. G. Zhang, Q. G. Wu, J. Li. “Synergetic Effects of Blended Materials for Lithium-ion Batteries”, *Science China*

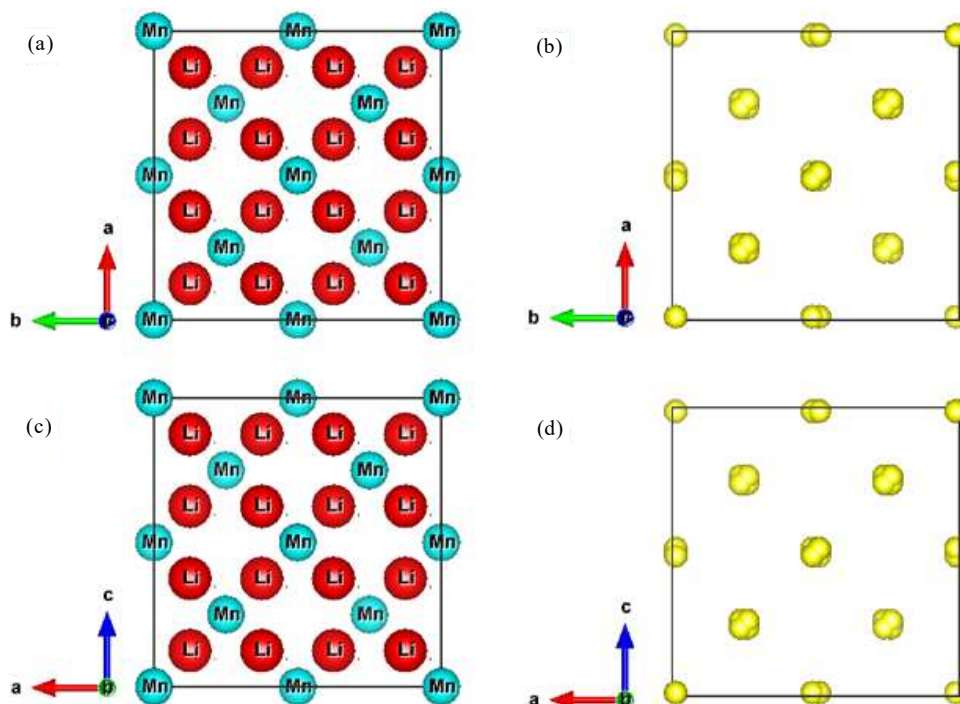


Figure 4. Simulation of the atom arrangement in the ideal LiMn_2O_4 spinel phase [15]. (a). Distribution of Mn and Li atoms in the viewpoint of $\{001\} \langle 100 \rangle$ (b). Distribution of O atoms in the viewpoint of $\{001\} \langle 100 \rangle$ (c). Distribution of Mn and Li atoms in the viewpoint of $\{010\} \langle 001 \rangle$ (d). Distribution of O atoms in the viewpoint of $\{010\} \langle 001 \rangle$.

- Technological Sciences*, Vol. 59 (9), pp. 1370-1376, Sep. 2016.
- [3] E. Y. Zhao, X. Q. Yu, F. W. Wang, H. Li. "High-capacity Lithium-rich Cathode Oxides with Multivalent Cationic and Anionic Redox Reactions for Lithium-ion Batteries", *Science China Chemistry*, Vol. 60 (12), pp. 1483-1493, Dec. 2017.
- [4] F. Marchini, E. J. Calvo, F. J. Williams. "Effect of the Electrode Potential on the Surface Composition and Crystal Structure of LiMn_2O_4 in Aqueous Solutions", *Electrochimica Acta*, Vol. 269, pp. 706-713, Feb. 2018.
- [5] J. Y. Zhang, J. X. Shen, T. L. Wang, C. B. Wei, Y. Ma, C. F. Zhu, Y. Z. Yue. "Improvement of Capacity and Cycling Performance of Spinel LiMn_2O_4 Cathode Materials with TiO_2 -B Nanobelts", *Electrochimica Acta*, Vol. 111, pp. 691-697, Aug. 2013.
- [6] L. X. Zhang, Y. Z. Wang, H. F. Jiu, Y. L. Wang, Y. X. Sun, Z. Z. Li. "Controllable Synthesis of Co-doped Spinel LiMn_2O_4 Nanotubes as Cathodes for Li-ion Batteries", *Electron. Matter. Lett.*, Vol. 10 (2), pp. 439-444, Mar. 2014.
- [7] M. Wang, M. Yang, X. Y. Zhao, L. Q. Ma, X. D. Shen, G. Z. Chao. "Spinel $\text{LiMn}_{2-x}\text{Si}_x\text{O}_4$ ($x < 1$) Through Si^{4+} Substitution as a Potential Cathode Material for Lithium-ion Batteries", *Science China Materials*, Vol. 59 (7), pp. 558-566, Jul. 2016.
- [8] J. H. Yao, L. T. Lv, C. Q. Shen, P. J. Zhang, K. F. Aguey-Zinsou, L. B. Wang. "Nano-sized Spinel LiMn_2O_4 Powder Fabricated via Modified Dynamic Hydrothermal Synthesis", *Ceramics International*, Vol. 39 (3), pp. 3359-3364, Apr. 2013.
- [9] C. G. Han, C. Y. Zhu, G. Saito, T. Akiyama, "Clycine/Sucrose Based Solution Combustion Synthesis of High-Purity LiMn_2O_4 with Improved Yield as Cathode Materials for Lithium-ion Batteries", *Advanced Powder Technology*, Vol. 26 (2), pp. 665-671, Mar. 2015.
- [10] H. W. Zhou, X. N. Ding, Z. Yin, G. F. Xu, Q. R. Xue, J. L. Li, S. Q. Jiao, X. D. Wang. "Fabrication and Electrochemical Characteristics of Electrospun LiMn_2O_4 Nanofiber Cathode for Li-ion Batteries", *Materials Letters*, Vol. 117, pp. 175-178, Nov. 2013.
- [11] G. M. Song, Y. J. Wang, Y. Zhou. "Synthesis of Al-doped LiMn_2O_4 Spinels by Mechanical Alloying and Rotary Heating", *Journal of Materials Science Letters*, Vol. 39, pp. 357-360, Jul. 2003.
- [12] J. W. Zhang, X. Guo, S. M. Yao, X. P. Qiu. "High Capacity Lithium-Manganese-Nickel-Oxide Composite Cathodes with Low Irreversible Capacity Loss and Good Cycle Life for Lithium Ion Batteries", *Science China Chemistry*, Vol. 59 (11), pp. 1479-1485, Nov. 2016.
- [13] S. Douafer, H. Lahmar, M. Benamira, G. Rekhila, M. Trari. "Physical and Photoelectrochemical Properties of the Spinel LiMn_2O_4 and its Application in Photocatalysis", *Journal of Physics and Electrochemistry of Solids*, Vol. 118, pp. 62-67, Jul. 2018.
- [14] C. Suryanarayana and M. Grant Norton. *X-ray Diffraction: a Practical Approach*. Plenum Press, New York, 1998.
- [15] E. Talik, A. Zalog, D. Skrzypek, A. Guzik, P. Zajdel, M. Michalska, L. Lipinska. " LiMn_2O_4 Nanocrystalline Electrode Materials", *Crystal Research and Technology*, Vol. 47 (3), pp.351-362, Feb. 2012.
- [16] J. B. Nelson and D. P. Riley. "An Experimental Investigation of Extrapolation Methods in the Derivation of Accurate Unit-cell Dimensions of Crystals", *Proc. Phys. Soc.*, Vol. 57 (160), pp. 160-177, Dec. 1944.

